



Index of refraction, Rayleigh scattering length, and Sellmeier coefficients in solid and liquid argon and xenon



Emily Grace ^{*}, Alistair Butcher, Jocelyn Monroe, James A. Nikkel

Royal Holloway, University of London, Department of Physics, Egham, Surrey TW20 0EX, UK

ARTICLE INFO

Keywords:

Rayleigh scattering
Index of refraction
Liquid argon
Liquid xenon
Solid argon
Solid xenon

ABSTRACT

Large liquid argon detectors have become widely used in low rate experiments, including dark matter and neutrino research. However, the optical properties of liquid argon are not well understood at the large scales relevant for current and near-future detectors. The index of refraction of liquid argon at the scintillation wavelength has not been measured, and current Rayleigh scattering length calculations disagree with measurements. Furthermore, the Rayleigh scattering length and index of refraction of solid argon and solid xenon at their scintillation wavelengths have not been previously measured or calculated. We introduce a new calculation using existing data in liquid and solid argon and xenon to extrapolate the optical properties at the scintillation wavelengths using the Sellmeier dispersion relationship.

© 2017 Published by Elsevier B.V.

1. Introduction

Liquid nobles such as argon and xenon are used many particle detector experiments including neutrino detectors and low-background dark matter detectors. This family of detectors relies on the scintillation light produced by nobles when exposed to external radiation. Understanding such signal in the detectors relies on a precise optical model to simulate the path of the scintillation light between production and detection in the thermal conditions of the detector medium. Key ingredients of this optical model are the index of refraction n and the scattering length, which depends strongly on n . The index of refraction has been measured at the scintillation wavelength of 178 nm in liquid xenon, but not yet in liquid argon. These properties are not well known, and indeed calculations differ from measurements by up to 30%. The state of current knowledge about the index of refraction and scattering length in argon and xenon is reviewed in Section 1.1. This difference is more impactful in larger detectors.

Knowledge of the scattering length in liquid nobles is becoming increasingly important as detectors get larger. In the past decade most liquid argon detectors were small prototypes, where the optical path length was often much shorter than the scattering length and therefore scattering was not a significant effect. In contrast, current and planned detectors are large. Presently constructed are the DarkSide 50 (50 kg) [1], ArDM (1 ton) [2], MicrobooNE (170 tons) [3], ICARUS (760 tons) [4], DEAP3600 (3600 kg), and MiniCLEAN (360 kg). Planned

are protoDUNE (770 tons) [5], DarkSide 20k (20k kg) [6], and DUNE (17,000 tons) [7]. The drift length in these detectors range from 1 to 8 m.

1.1. Survey of previous literature

The existing measurements of the index of refraction in argon and xenon are summarized in Section 1.1.1. Historically, measurements of the index of refraction at temperatures at or above the triple point have been used in calculations to predict the value below the triple point, as described in Section 1.1.2. These calculations predict the wavelength dependence, which has been used in experiment simulations [8,9] to model the propagation of photons produced at the scintillation wavelengths in liquid noble targets.

1.1.1. Measurements

- Sinnock and Smith [10] measured the index of refraction as a function of wavelength at temperatures between 90 and 20 K in argon and at temperatures between 80 and 178 K in xenon. These measurements were made in the wavelength range 350–650 nm. The typical experimental error reported is $\pm 0.5\%$. (Data from [10] is shown in Figs. 1 and 3.)
- Bideu-Mehu et al. [11] measured the index of refraction of room temperature argon and xenon gas between the wavelengths of 140 and 174 nm and used these values to find the Sellmeier

^{*} Corresponding author.

E-mail address: Emily.Williams.2012@live.rhul.ac.uk (E. Grace).

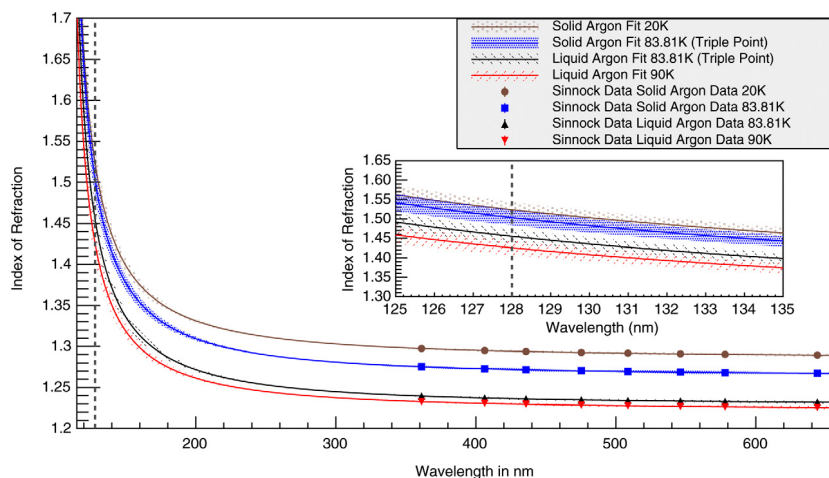


Fig. 1. Calculated index of refraction vs. wavelength (nm) for solid and liquid argon. Source: The points show the data from Ref. [10].

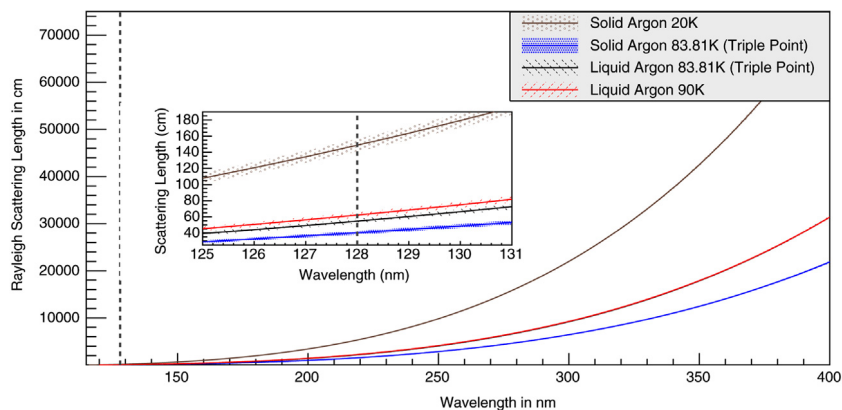


Fig. 2. Calculated Rayleigh scattering length (cm) vs. wavelength (nm) for solid and liquid argon.

coefficients for the gas based Sellmeier [12] equation. The typical experimental error reported is $\pm 0.1\%$

- Ishida et al. [13] measured the attenuation length of liquid xenon and argon at the wavelengths of 178 nm and 128 nm respectively. They found values of 66 ± 3 cm for argon at 87 K and 29 ± 2 cm for xenon at 196 K.
- Solovov et al. [14] measured the index of refraction and attenuation length of liquid xenon at the triplet point and obtained a value of 1.69 ± 0.02 for the index of refraction and 36 ± 2 cm for the attenuation length.
- The ArDM collaboration published an in situ measurement of the attenuation length of liquid argon in the detector. This yield a measurement of 52 ± 7 cm [15].

1.1.2. Calculation

Seidel et al. calculated the Rayleigh scattering length for liquid argon and xenon. Seidel's calculated values were 90 cm for argon and 30 cm for xenon (the authors did not include the error on their calculation). The calculated Rayleigh scattering length agrees within errors with the measured values for xenon from Ishida et al. The calculation is robust in the sense that the xenon value was calculated using the measured value of the index of refraction in liquid xenon, with no extrapolation in temperature or pressure. In the case of argon, Seidel et al. [16] used STP gas data from Bideu-Mehu et al. [11] to extrapolate the index of refraction at the scintillation wavelength. This value was adjusted according to the density change from liquid to solid, but any

temperature dependence was neglected, a decision made based on the gas measurements by Achtermann et al. [17].

2. Rayleigh scattering length calculation dependence on index of refraction

In the following calculation, the temperature dependence is allowed. Similarly to Seidel et al., we then fit the temperature and density-controlled data from Sinnock and Smith [10] to find the Sellmeier coefficients, which enter the calculation of the index of refraction and thereby the Rayleigh scattering length.

Rayleigh scattering is the process of light elastically scattering off of particles smaller than the wavelength of light. The length of travel for a photon through a medium before Rayleigh scattering is strongly dependent on the wavelength of the light as well as the optical properties of the material. The Rayleigh scattering equation for liquids and solids is

$$l^{-1} = \frac{16\pi^3}{6\lambda^4} \left[kT\rho\kappa_T \left(\frac{(n^2 - 1)(n^2 + 2)}{3} \right)^2 \right], \quad (1)$$

where l is the scattering length, λ is the wavelength of light, n is the index of refraction corresponding the wavelength of light, T is temperature, ρ is density, and κ_T the isothermal compressibility. For this equation to be valid the index of refraction should be evaluated at the temperature, density and wavelength [18]. There are also material dependent correction factors than can be added to Eq. (1) that do not apply in the case of nobles [19]. This expression for Rayleigh scattering length will be used in the extrapolations in Section 3.

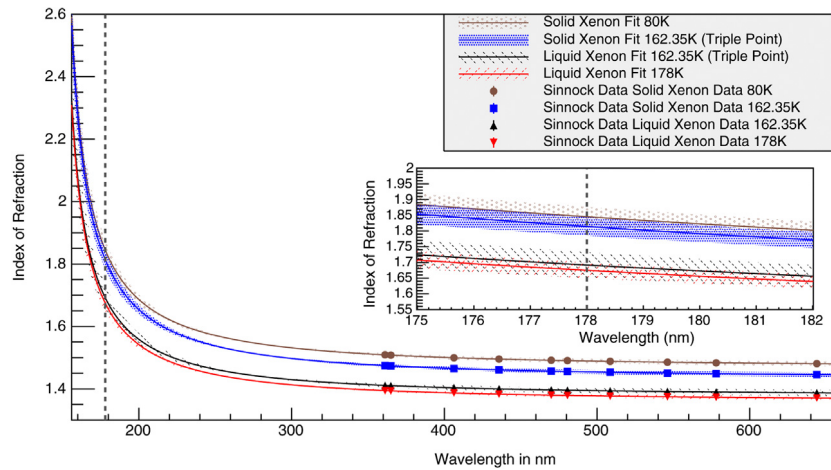


Fig. 3. Calculated index of refraction vs. wavelength (nm) for solid and liquid xenon.
Source: The points show the data from Refs. [14] and [10].

Table 1

Scintillation and resonance wavelengths of argon and xenon. Argon UV resonance value obtained from [22], xenon UV resonance obtained from [11] and argon and xenon IR resonances sourced from [23]. Xenon scintillation length obtained from [14] and argon scintillation length obtained from [24].

Element	Scintillation λ (nm)	UV resonance λ (nm)	IR resonance λ (nm)
Argon	128	106.6	908.3
Xenon	178	146.9	827.0

2.1. Index of refraction

The Sellmeier dispersion relation for liquids and solids at constant temperature and density [12,20], is used to wavelength λ to the index of refraction n . This relation is

$$n^2 = a_0 + \sum_i \frac{a_i \lambda^2}{\lambda^2 - \lambda_i^2}. \quad (2)$$

In this case a_0 is a Sellmeier coefficient that accounts for the effect of UV resonances not included in the sum and a_i are the Sellmeier coefficients that correspond with the resonances, occurring at wavelength λ_i . The Sellmeier dispersion equation was derived from the Lorentz–Lorenz equation [18,21] and the coefficients (a_0, a_i) are experimentally determined for a given medium. The scintillation wavelength of argon and xenon is between the UV and IR resonance peaks (shown in Table 1), thus the following equation is sufficient for fitting the coefficients in the range of wavelengths around the scintillation wavelength,

$$n^2 = a_0 + \frac{a_{UV} \lambda^2}{\lambda^2 - \lambda_{UV}^2} + \frac{a_{IR} \lambda^2}{\lambda^2 - \lambda_{IR}^2}, \quad (3)$$

where λ_{UV} corresponds to the closest or first UV resonance and λ_{IR} corresponds to the closest or first IR resonance.

3. Calculation expanding in temperature and state

In the calculations done by Seidel, to predict the index of refraction and scattering length in liquid nobles, the dispersion equation for gases was used to fit the gas data from [11] for the Sellmeier coefficients. We update this calculation by fitting the Sellmeier coefficients (Eq. (3)) to liquid and solid data from [10], to find the respective scattering lengths in liquid and solid argon and xenon. The Sellmeier coefficients resulting from the fit can be found in Table 2.

3.1. Fit verification

Solovov et al. [14] measured the index of refraction of the scintillation wavelength of liquid xenon at the triple point of temperature 162 K.

Table 2

Argon and Xenon Sellmeier coefficients calculated using data from [10]. 83.81 K is the argon triple point and 162.35 K is the xenon triple point. These coefficients are for egs units.

T (K)	a_0	a_{UV}	a_{IR}
Solid argon			
20	1.4 ± 0.1	0.30 ± 0.09	0.0011 ± 0.007
83.81	1.3 ± 0.1	0.29 ± 0.09	0.00087 ± 0.007
Liquid argon			
83.81	1.24 ± 0.09	0.27 ± 0.09	0.00047 ± 0.007
90	1.26 ± 0.09	0.23 ± 0.09	0.0023 ± 0.007
Solid xenon			
80	1.6 ± 0.3	0.6 ± 0.2	0.001 ± 0.03
162.35	1.4 ± 0.2	0.6 ± 0.2	0.0008 ± 0.03
Liquid xenon			
162.35 ^a	1.5 ± 0.02	0.38 ± 0.01	0.009 ± 0.01
178	1.4 ± 0.2	0.4 ± 0.2	0.002 ± 0.02

^a This fit includes the point from [14].

The liquid triple point data from [10] was fit with Eq. (3) and used this fit to extrapolate to the scintillation wavelength. The extrapolation error was calculated using the covariance matrix, as described in [25]. The predicted value is 1.69 ± 0.04 predicts the measured value of 1.69 ± 0.02 .

3.2. Results

The Sellmeier coefficients obtained by fitting the data from Sinnock and Smith [10] were then used to extrapolate the index of refraction and Rayleigh scattering length at the scintillation wavelengths. The new calculated values of the index of refraction and Rayleigh scattering length vs. wavelength are shown in Figs. 1 and 2 for liquid argon, and in Figs. 3 and 4 for xenon in both solid and liquid phases. The results of this new calculation are summarized in Table 3.

4. Conclusion

This calculation has produced the first prediction for the Rayleigh scattering length in liquid argon and xenon for which the Sellmeier dispersion constants are fit from measurements at the same temperature and state. This is the first calculation of the scattering length in solid argon and xenon. This analysis used the data from Sinnock et al. [10] to extrapolate the wavelength dependent index of refraction through argon at constant temperature and state. Using this index of refraction,

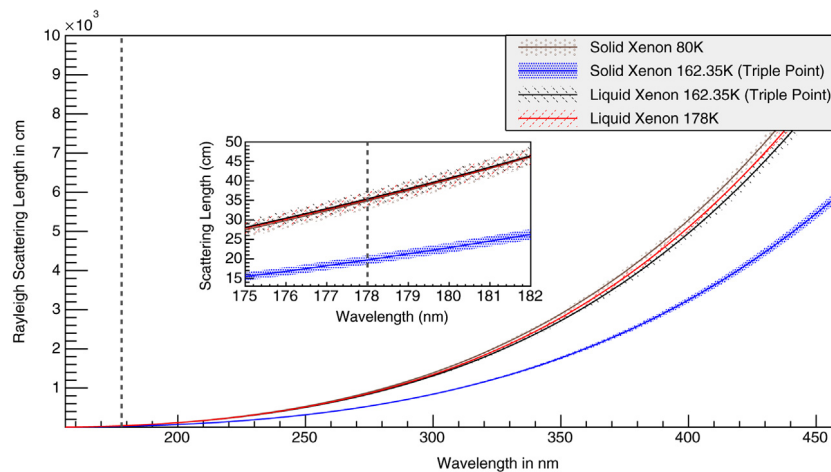


Fig. 4. Calculated Rayleigh scattering length (cm) vs. wavelength (nm) for solid and liquid xenon.

Table 3

This a summary of the results of the extrapolations made by fitting the Sinnock data at the triple point with the Sellmeier equation. Both the liquid and solid triple point values are included. These values are compared with previous calculations and measurements. The previous index of refraction and Rayleigh scattering length calculation come from [16]; error bars were not included in the original work. The previous argon scattering length measurements come from [13] and the previous xenon index of refraction measurement and attenuation length is from [14].

Element	n			l (cm)		
	This calculation	Previous calculation	Previous measurement	This calculation	Previous calculation	Previous measurement
Liquid argon	1.45 ± 0.07	1.37	N/A	55 ± 5	90	66 ± 3
Liquid xenon	1.69 ± 0.04	1.68	1.69 ± 0.02	35 ± 2	30	36 ± 2
Solid argon	1.50 ± 0.07	N/A	N/A	40 ± 4	N/A	N/A
Solid xenon	1.81 ± 0.03	N/A	N/A	20 ± 1	N/A	N/A

the Rayleigh scattering length in liquid argon at 90 K is calculated to be 60 ± 6 and 55 ± 5 cm. The extrapolation of the index of refraction at 90 K is within error of the value measured by Ishida et al. [13] unlike the extrapolated value by Seidel et al. [16]. The accuracy of the extrapolation method was tested against a measured point in xenon and we were able to predict the value within experimental error.

ArDM used the results of this calculation to update the optical simulation. Using this, an in situ measurement of the attenuation length was made with result of 52 ± 7 cm [15]. This is within error the predicted value.

The data taken by Sinnock et al. [10] also gave us the opportunity to produce values for the index of the refraction and Rayleigh scattering lengths of solid argon and xenon at different temperatures at the scintillation wavelengths. These values may be useful in future detectors or experiments that take advantage of the scintillation properties of these elements in a solid state. All of the results for the index of refraction and Rayleigh scattering length are collected in Table 3.

Acknowledgments

We acknowledge support from the European Research Council Project ERC StG 279980, the UK Science and Technology Facilities Council (STFC) grant ST/K002570/1, the Leverhulme Trust grant number ECF-20130496, and STFC and SEPNet Ph.D. studentship support.

References

- [1] P. Agnes, I. Albuquerque, T. Alexander, A. Alton, D. Asner, H. Back, B. Baldin, K. Biery, V. Bocci, G. Bonfini, et al., Effect of low electric fields on alpha scintillation light yield in liquid argon, 2016, arXiv Preprint arXiv:1611.00241.
- [2] A. Rubbia, Ardm: a ton-scale liquid argon experiment for direct detection of dark matter in the universe, in: Journal of Physics: Conference Series, Vol. 39, IOP Publishing, 2006, p. 129 1.
- [3] B.J. Jones, The status of the microboone experiment, in: Journal of Physics: Conference Series, Vol. 408, IOP Publishing, 2013, p. 012028.
- [4] M. Antonello, P. Aprili, B. Baiboussinov, M.B. Ceolin, P. Benetti, E. Calligarich, N. Canci, S. Centro, A. Cesana, K. Cieřlik, et al., Measurement of the neutrino velocity with the icarus detector at the cngs beam, Phys. Lett. B 713 (1) (2012) 17–22.
- [5] N. Charitonidis, I. Efthymiopoulos, Y. Karyotakis, Beam performance and instrumentation studies for the protodune-dp experiment of cenf, 2016, arXiv Preprint arXiv:1607.07612.
- [6] S. Davini, P. Agnes, L. Agostino, I. Albuquerque, T. Alexander, A. Alton, K. Arisaka, H. Back, B. Baldin, K. Biery, et al., The darkside awakens, in: Journal of Physics: Conference Series, Vol. 718, IOP Publishing, 2016, p. 042016.
- [7] R. Acciarri, M. Acerro, M. Adamowski, C. Adams, P. Adamson, S. Adhikari, Z. Ahmad, C. Albright, T. Alion, E. Amador, et al. Long-baseline neutrino facility (lbnf) and deep underground neutrino experiment (dune) conceptual design report, volume 4 the dune detectors at lbnf, 2016, arXiv Preprint arXiv:1601.02984.
- [8] F.N.A. Laboratory, United States. Department of Energy. High Energy Physics Division, United States. Department of Energy. Office of Scientific, United States. Department Information, Technical The Liquid Argon Software Toolkit (LARSoft): Goals, Status and Plan United States. Department of Energy. High Energy Physics Division, 2016. URL <https://books.google.com/books?id=k1tqnQAACAAJ>.
- [9] S. Agostinelli, et al., GEANT4: A Simulation toolkit, Nucl. Instrum. Meth. A506 (2003) 250–303. [http://dx.doi.org/10.1016/S0168-9002\(03\)01368-8](http://dx.doi.org/10.1016/S0168-9002(03)01368-8).
- [10] A.C. Sinnock, B.L. Smith, Refractive indices of the condensed inert gases, Phys. Rev. 181 (1969) 1297–1307.
- [11] A. Bideau-Mehu, Measurement of refractive indices of neon, argon, krypton and xenon in the 253.7 140.4 nm wavelength range. dispersion relations and estimated oscillator strengths of the resonance lines, J. Quant. Spectrosc. Radiat. Transfer 25 (1981) 395–402.
- [12] M. Born, E. Wolf, Principles of Optics, seventh ed., Cambridge University Press, 1999.
- [13] N. Ishida, M. Chen, T. Doke, K. Hasuie, A. Hitachi, M. Gaudreau, M. Kase, Y. Kawada, J. Kikuchi, T. Komiyama, K. Kuwahara, K. Masuda, H. Okada, Y. Qu, M. Suzuki, T. Takahashi, Attenuation length measurements of scintillation light in liquid rare gases and their mixtures using an improved reflection suppresser, Nucl. Instrum. Methods Phys. Res., Sect. A 384 (23) (1997) 380–386.
- [14] V. Solovov, V. Chepel, M. Lopes, A. Hitachi, R.F. Marques, A. Policarpo, Measurement of the refractive index and attenuation length of liquid xenon for its scintillation light, Nucl. Instrum. Methods Phys. Res., Sect. A 516 (23) (2004) 462–474.
- [15] J. Calvo, C. Cantini, P. Crivelli, M. Daniel, S. DiLuise, A. Gendotti, S. Horikawa, L. Molina-Bueno, B. Montes, W. Mu, et al., Measurement of the attenuation length of argon scintillation light in the ardm lar tpc, 2016, arXiv Preprint arXiv:1611.02481.
- [16] G. Seidel, R. Lanou, W. Yao, Rayleigh scattering in rare-gas liquids, Nucl. Instrum. Methods Phys. Res., Sect. A 489 (13) (2002) 189–194.
- [17] H. Achtermann, et al., Experimental determination of the refractivity virial coefficients of atomic gases., Chem. Phys. 98 (1993) 2308–2319.

- [18] L. Landau, E. Lifshitz, *Electrodynamics of Continuous Media*, Vol. 8, Pergamon Press, 1960.
- [19] A. Morel, Optical properties of pure water and pure sea water, *Opt. Asp. Oceanogr.* 1 (1974) 1–24.
- [20] P. Schiebener, J. Straub, J.L. Sengers, J. Gallagher, Refractive index of water and steam as function of wavelength, temperature and density, *J. Phys. Chem. Ref. Data* 19 (3) (1990) 677–717.
- [21] H.A. Lorentz, Ueber die beziehung zwischen der fortpflanzungsgeschwindigkeit des liches und der krperdichte, *Wiedem. Ann.* 9 (1880) 641–665.
- [22] A.L. Lane, A. Kuppermann, Argon resonance line lamp for vacuum ultraviolet photochemistry, *Rev. Sci. Instrum.* 39 (1) (1968) 126–127.
- [23] S. Arai, T. Oka, M. Kogoma, M. Imamura, Near infrared absorptions of neon, argon, krypton, and xenon excited diatomic molecules, *J. Chem. Phys.* 68 (10) (1978) 4595–4603.
- [24] E. Aprile, A. Bolotnikoc, A. Bolozdynaya, T. Doke, *Noble Gas Detectors*, first ed., Wiley-VCH, 2006.
- [25] J. Tellinghuisen, Statistical error propagation, *J. Phys. Chem. A* 105 (2001) 3917–3921.